

Presenting asphalt mixtures flow number prediction model using gyratory curves

H. Ziari^{1,*}, H. Divandari²

Received: July 2012, Revised: December 2012, Accepted: March 2013

Abstract

Pavement permanent deformations due to lack of shear strength in mixture are a major reason of rutting. Any simple test to determine mixtures resistance to permanent deformation isn't distinguished in the 1st level of SUPERPAVE mix design method and prevalent methods for evaluating mixture rut resistance are expensive and time-consuming. Two aggregate types, gradations, asphalt cements and filler types were used in this research to present a prediction model for rutting based on flow number. A mathematical model to estimate flow number of dynamic creep test was developed using model parameters and gyratory compaction slope. The model is validated using Neural Network and Genetic Algorithm and makes it possible to evaluate mixtures shear strength while optimum asphalt content is being determined in laboratory. So not only there is no need to expensive test instruments of rutting or dynamic creep but a remarkable time saving in mix design procedure is achievable.

Keywords: Rutting, Gyratory, Dynamic creep, Flow number, Shear stress curve.

1. Introduction

Increasing loading cycles on pavement leads to cumulative raise in permanent deformation and rutting as a surface depression in wheel path which can cause hydroplaning, reduce pavement drainage capacity, make moisture based deterioration growing rate faster, pavement thickness decreases in rutted zone and finally increase fatigue cracking in flexible pavements [1]. Mentioned parameters introduce rutting as an expensive flexible pavement deterioration mechanism [2]. Rutting could be recognized as a result of mixture volume decrease (pavement consolidation due to traffic (figure 1)), asphalt permanent deformation in constant volume (Plastic deformations due to normal shear stress in mixture (figure 2)) or a combination of them [3]. Another type of rutting is known which is due surface layer abrasion. Surface permanent deformation have the most share among various rutting causes, so considering it in mix design procedure seems essential [3,4].

Various laboratory methods are introduced to evaluate pavement permanent deformation which direct shear, repeated

shear at constant height, dynamic shear modulus test, creep and rutting test. Austria, France, Hungary, Romania and Switzerland use LCPC (Laboratoire Central des Ponts et Chaussées) and Finland, Sweden and Australia use Dynamic creep for rutting evaluation.

The pressure of 300 kPa is applied to specimen in a cycle with 500ms loading and 1500 ms rest at 50°C in dynamic creep test. Drawing specimen cumulative permanent deformation curve versus loading cycles will produce the illustrated curve of figure 3 with three main stages. It is proved that the cycle in which territory phase is started (Fn) (Flow Number) is related to mixture rutting resistance directly [6,7].

This is a time-consuming test and UTM (Universal Testing Machine) which is used as the creep test instrument is expensive and needs skillful operator. So developing a method to distinguish asphalt mixture shear strength in a non-expensive and fast method is necessary.

2. Problem Definition

2.1. Research Target and Essence

Compaction as the most important issue on aggregates structure and positioning has considerable effect on mixtures rut and permanent deformation resistance [9]. It is proved that aggregates rotary or transitive in asphalt mixture due to inadequate compaction will cause permanent deformation

* Corresponding Author: h.ziari@iust.ac.ir

1 Department of Civil Engineering, Iran University of Science and Technology, Tehran, Iran.

2 Islamic Azad University, Nowshahr Branch, Department of Engineering, Nowshahr, Iran.

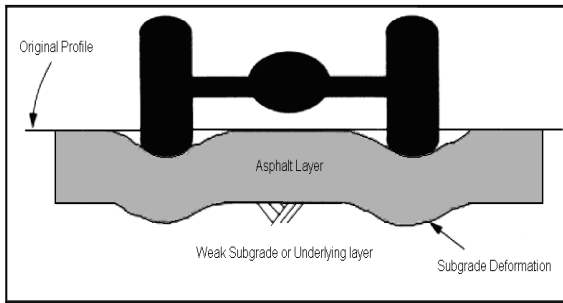


Fig. 1 Rutting due to bottom layers consolidation [5]

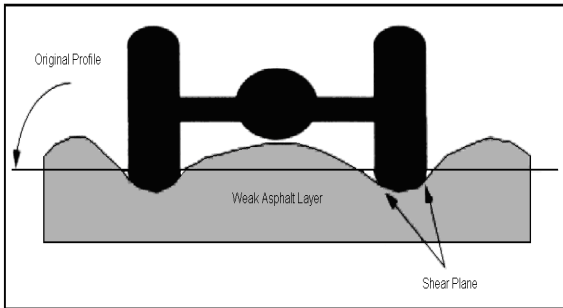


Fig. 2 Rutting due to lack of shear strength in asphalt mixture [5]

along shear planes [10]. On the other hand a weakness point of marshal method which is most applied method of compaction and mix design in Iran is compacting method which doesn't provide a fair simulation according to the researches [11]. Hence gyratory compaction machine (GCM) is used in SUPERPAVE mix design method after 40 years research on rotational compaction method by SHRP. This mix design method involves three levels which are divided by load and traffic. The first level is considered for traffic less than 10^6 ESALs (Equivalent Single Axle Loads) which composes of volumetric analysis and simple tests. Being simple and economical issues make this level interesting for engineers, but lack of performance tests is remarkable here. Simple methods for evaluating asphalt mixture workability should be developed to complete this level.

Asphalt mixtures with various aggregates, asphalt cements, gradation and filler were prepared and a model to predict flow number and consequently rutting resistance were developed after determining OAC for each group and performing dynamic creep test. As a result of this study mixture rutting

potential is predictable in a short time with low cost in laboratory simultaneously with preparing them.

2.2. Literature Review

Lack of a test in 1st level of SUPERPAVE mix design to predict rutting of asphalt mixtures lead a lot of researches focus on this issue in FHWA (Federal Highway Administration), NCHRP (National Cooperative Highway Research Program) and FAA (Federal Aviation Administration) [12]. Other studies in this field using GCM output information will be stated in the following part.

2.2.1. Studies on Compaction Slope of SGC (Superpave Gyratory Compactor)

The idea of using SGC compaction slope was developed for the first time in 2000 [13]. Later studies stated that compaction slope is only an aggregates internal friction property [14]. But according to Mohr-Coulomb formula, shear stress (τ) is a function of cohesion (C) and internal friction angle (Φ). Although other studies proofed SGC compaction slope effect on rutting, but this parameter can't be used singly to predict asphalt shear strength performance.

$$\tau = C + \sigma_n \times \tan(\phi) \quad (1)$$

2.2.2. Studies Considered a Part of Compaction Slope Curve

Researches define various indexes for asphalt rutting resistance with studying volumetric mass versus curve. TDI (Terminal Densification Index) which is assumed as compaction curve integral from 4% to 2% voids was one of them. DEI (Densification Energy Index) was defined as 8% to 4% voids in mentioned curve and CEI (Compaction Energy Index) as compaction start to 8% voids integral (Figure 4). Studies showed models based on these indexes were affected by aggregates positioning in molds greatly and wide tests showed this models aren't reliable. [15,16].gyration

2.2.3. Studies on Shear Parameters in Compaction

Gyratory shear strength, gyration number corresponding to maximum shear and gyratory shear slope were defined using gyratory shear curve. Researches performed in Florida and Michigan Universities although there is a relation between APA (Asphalt Pavement Analyzer) rut depth and these parameters but presented models didn't show good relation and aren't applicable [17].

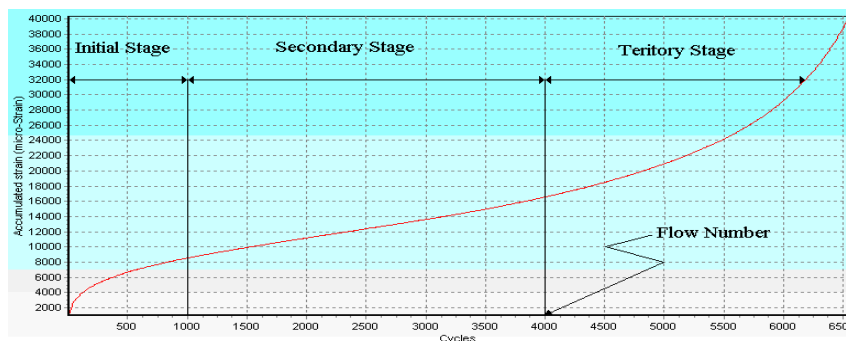


Fig. 3 Three stages of cumulative strain curve versus loading cycles in dynamic creep test [8]

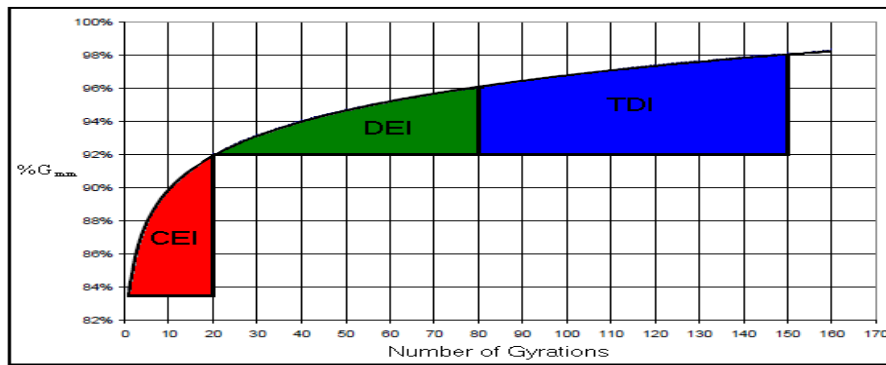


Fig. 3 Energy indices in density variations vs. gyratory gyration number curve [18]

2.3. Research Assumptions

Although asphalt rutting is derived from cumulative deformation of base and subbase layers consolidation, abrasion and permanent deformation in asphalt layer but the main reason of rutting is asphalt permanent deformation [4]. This parameter was studied in this research under 50°C temperature. To consider design requirements asphalt mixtures were prepared using OAC ($\pm 0.5\%$). Materials were similar from shape and aggregate texture issues and all specimens were prepared in a constant situation.

3. Methodology

3.1. Materials Selection and Tests

RudehenAsbcheran mine (east of Tehran) and Rivand mine (Sabzevar) were used for limestone and silica aggregates source respectively. Minimum Percentage of Fracture, Maximum Abrasion, Maximum Water Absorption, Minimum Adhesion in Bitumen-Aggregate System, Minimum Sand Equivalent and Minimum Sulfate Soundness Value tests results were in the

standard range. Saveh mine rock powder and Qom limestone powder passed from 0.075mm sieve were used as two filler types in specimen preparation procedure. PI and Hydrometry test results located in standard range either. Asphalt cement was supplied from Pasargad Oil Company in tow types of AC60-70 and AC85-100. Penetration, SayboltForol Viscosity, Softening Point, Ignition Point, Specific Gravity, Weight Loss and Ductility performed for both types and results passed Code234 (Iranian Pavement Code) requirements [19]

3.2. Optimum Asphalt cement Content

3.2.1. Gradation

Middle range of number 4 and 5 continuous gradations were used according to table 1.

3.2.2. OAC Determination and Specimen Naming

According to various types of aggregates, gradation, filler and asphalt cement, 288 specimens were prepared for OAC using marshal method and finally 16 optimum asphalt contents were determined as table 2. Combination of two letters and two numbers was used for specimen naming. Left to right, first

Table 1 Aggregates gradation for Binder and Topka layers [4]

Sieve Specification			Number 4 Continuous Gradation			Number 5 Continuous Gradation		
Sieve			Passed Range	Passed	Remained	Passed Range	Passed	Remained
mm	Number	Inches	Weight (%)	Ave. Weight (%)	Weight (%)	Weight (%)	Ave. Weight (%)	Weight (%)
19	-	(3/4)	100	100	0	-	-	-
12.5	-	(1/2)	90-100	95	5	100	100	0
9.5	-	(3/8)	-	-	-	90-100	95	5
4.75	4	-	44-74	59	36	55-85	70	25
2.36	8	-	28-58	43	16	32-67	49/5	20/5
1.18	16	-	-	-	-	-	-	-
0.6	30	-	-	-	-	-	-	-
0.3	50	-	5-21	13	30	7-23	15	34/5
0.15	100	-	-	-	-	-	-	-
0.075	200	-	2-10	6	7	2-10	6	9

Table 2 Determined OAC for 16 various asphalt mixture combination

Limestone Specimen Specification	A4P6	A4P8	A5P6	A5P8	A4A6	A4A8	A5A6	A5A8
OBC	5.81	5.70	5.92	5.80	6.16	5.90	6.24	6.00
Silica Specimen Specification	S4P6	S4P8	S5P6	S5P8	S4A6	S4A8	S5A6	S5A8
OBC	5.05	4.96	5.24	5.02	5.40	5.15	5.45	5.25

character shows aggregate type (S for silica base aggregate and A for limestone base aggregate), second character is a number shows gradation number (4 for gradation number 4 and 5 for gradation number 5), third character is the filler type (P for rock powder and A for limestone powder) and the fourth character is the asphalt cement type (6 for AC60-70 and 8 for AC85-100).

3.3. Preparing Specimens for Tests

3.3.1. Choosing Gyration Number

Gyratory Compaction Machine was used for compacting specimens. 8, 95 and 150 gyrations were chosen for N_{ini} , N_{des} and N_{max} respectively according to table 3 for ESALs equal to 106.

3.3.2. Determining Number of Specimens for Research

To perform rutting test, due to various parameters, 144 specimens were prepared totally with OAC, 0.5% less and 0.5% more asphalt cement content with SGC. To validate test results 3 specimens were made for each similar condition.

3.1. Gyratory Parameters

3.4.1. Gyratory Shear Stress Modeling Parameters

Shear stress versus gyration number is one of the SGC output curves. To gain more parameters from gyratory output curves and since it is proved shear stress is related to rutting inversely, gyratory shear stress were modeled versus gyration number as independent parameter. Following logarithmic model seemed to be the best model after testing all models:

$$G_s = K_1 \ln(N) + K_2 \quad (2)$$

In which G_s is gyratory shear stress in a specific gyration of N while K_1 and K_2 are gyratory shear stress semi-log curve slope and y-intercept respectively.

In other words graphs such as figure 5 were drawn for all 144 specimens and the result of modeling is shown in table 4. As it is clear in this table more than 95.14% of models have more than 75% correlation coefficient.

Maximum shear (S_m) is the other variable which can be determined using presented model except K_1 and K_2 .

Table 3 N_{ini} , N_{des} and N_{max} in SGC [4]

ESALS 10^6	Maximum Design Temperature Average											
	< 39 °C			39-40 °C			41-42 °C			43-44 °C		
	N-initial	N-design	N-max	N-initial	N-design	N-max	N-initial	N-design	N-max	N-initial	N-design	N-max
<0.3	7	68	104	7	74	114	7	78	121	7	82	127
0.3-1	7	76	117	7	83	129	7	88	138	8	93	146
1-3	7	86	134	8	95	150	8	100	158	8	105	167
3-10	8	96	152	8	106	169	8	113	181	9	119	192
10-30	8	109	174	9	121	195	9	128	208	9	135	220
30-100	9	126	204	9	139	228	9	146	240	10	153	253
>100	9	143	235	10	158	262	10	165	275	10	172	288

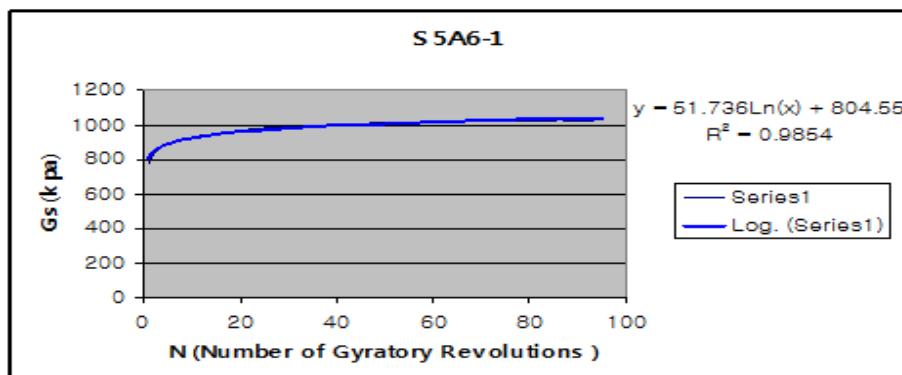


Fig. 5 Shear stress modeling versus gyration number (for one of the limestone specimens, gradation number 4, rock powder as the filler and 60-70 asphalt cement)

Table 4 Determining Correlation Coefficient of presented model for all gyratory shear stress curves (144 specimens)

R ² Range	Correlation Coefficient (R)						Total
	100-95	95-90	90-85	85-80	80-75	<75	
Number of Specimens	84	29	9	10	5	7	144
Percent	58.33	20.14	6.25	6.94	3.48	4.86	100

3.4.2. Compaction Slope Parameter

Specimen height is the other parameter measured by gyratory per cycle. Since specimen height is distinguished in each cycle, compaction slope can be determined using eq. 3 considering constant specimen weight and specimen cross section. Studies showed compaction slope is related to aggregates internal friction directly, so it can affect shear strength of mixture [20].

$$K = \frac{(\%G_{mm,Ndes} - \%G_{mm,Nini})}{[\log(N_{des}) - \log(N_{ini})]} * 100 \quad (3)$$

In which:

$$\%G_{mm,Ndes} = \frac{G_{mb}}{G_{mm}} \quad (4)$$

$$\%G_{mm,Nini} = \%G_{mm,Ndes} * \frac{h_{des}}{h_{ini}} \quad (5)$$

- $\%G_{mm,Ndes}$ and $\%G_{mm,Nini}$: Asphalt mixture maximum specific gravity percent at initial gyration and design gyration respectively,
- h_{ini} and h_{des} : Specimen height in N_{ini} and N_{des} during compaction respectively,
- G_{mb} and G_{mm} : Bulk and maximum specific gravity respectively.

3.4.3. Other Parameters

Other parameters like air voids in initial and design gyration ($V_{a_{ini}}$ and $V_{a_{des}}$), gyration number in which maximum shear stress is given ($N-S_m$), Voids in mineral aggregates (VMA), height and density variations were determined for each specimens which only K , K_1 and S_m introduced as effective parameters in sensitivity analysis. (table 5)

3.5. Creep Test

Three creep tests were performed for each combination at 50°C, under 300 kpa pressure with 500 ms loading and 1500 ms rest using UTM-5 and flow number of each combination were determined [21]. The results could be seen in table 6.

4. Presenting Experimental Model

4.1. Developing a Model using SPSS19

Predicting a variable behavior using other variables behaviors is the target of regression. It means to recognize the relation between effective parameters (x) and affected parameters (y) and to ensure a meaningful correlation between variables and finally to estimate a variable using another one. Correlation Coefficient (R^2) is a parameter which illustrates a relation between model results and actual

Table 5 Analysis of variance (SPSS 19 Output)

ANOVA					
Model	Sum of Squares	df	Mean Square	F	Sig.
Regression	5.809E8	2	2.904E8	436.047	.000
1 Residual	87258037.990	131	666091.893		
Total	6.682E8	133			

results. Two assumptions are considered in regression as H_0 and H_1 :

$$\begin{cases} H_0: R = 0 \\ H_1: R \neq 0 \end{cases} \quad (6)$$

The aim is to reject H_0 assumption which sig F change coefficient is used for validation. Whatever this coefficient is less, R^2 meaningfulness is more and so the model is more validated. This coefficient should be less than 0.05 since reliability is considered as 95% in this model. Statistical analysis results of 144 data series in SPSS 19 is listed in table 7 and the model was gained as following:

According to tables 8 and 9, final model was presented as equation 7:

$$F_n = 743.562 K - 94.115 K_1 \quad (7)$$

In which:

F_n = Flow number from dynamic creep test

K = Gyratory Compaction Slope from Eq3

K_1 = Gyratory Shear Stress Curve Slope (Eq2)

As it can be understood from table 7, R for this model is 0.932 which is meaningful in 95% reliability level.

4.2. Validating the model using ANN

ANN (Artificial Neural Network) is a simulation of brain nerve and has learning, generalization, and decision making power like human's brain. In designing the network, after defining a dynamic system mechanism, the model is trained and system mechanism is saved in model memory, so this memory is used to estimate new cases. Neural networks have been used in various aspects of pavement engineering such as estimating asphalt dynamic and elasticity modulus [22,23], asphalt cement properties effect on asphalt features [24] and Mixture Compaction Quality Control [25].

A neural network is composed from several processors which are called neurons or nodes. Each neuron is connected to other neurons with oriented lines having specific weight. Weight shows the amount of information used by network to solve the problem. Neurons are organized in groups called layers. Generally there are two layers to connect network with out of it as input layer (to get input data) and output layer to transfer answers out of network. Other layers between these two layers are called hidden layers. Network input and output layer number depends on dependent and independent variables of the desired relation respectively. The model in this paper has two independent variables and one dependent variable, so the network has two input neurons and one output neuron (figure 6).

Figure 7 shows input (I) and output (O) and a hidden neuron structure. B and w parameters could be set up and f function type is selected by designer so the neuron output is desired. Determining b and w for total network is called network training. Network output is compared with actual observations and error is calculated in training process.

Table 6 Gyratory compactor and creep test results for 144 specimens

Limestone Specimen Specification	Difference with OAC	F _n	K	K ₁	K ₂	Maximum Shear (Sm)	Silica Specimen Specification	F _n	K	K ₁	K ₂	Maximum Shear (Sm)
1 A4P6		1225	10.560	61.387	787.630	1049	1 S4P6	320	8.281	54.606		803.12
2 A4P6	-0.5	2000	8.620	44.936	647.320	839	2 S4P6	620	7.909	54.593		835.41
3 A4P6		1300	10.747	64.181	774.380	1046	3 S4P6	2704	6.906	38.522		911.16
1 A4P6		5100	8.034	40.065	676.750	893	1 S4P6	664	8.632	60.530		825.94
2 A4P6	0.0	5250	10.161	28.635	845.770	977	2 S4P6	1872	7.676	37.358		923.89
3 A4P6		5000	10.713	40.814	839.350	1026	3 S4P6	788	8.718	56.609		835.55
1 A4P6		7375	8.869	47.824	815.980	1062	1 S4P6	684	8.945	58.899		843.50
2 A4P6	0.5	6900	7.743	44.735	658.330	870	2 S4P6	756	7.423	46.943		874.27
3 A4P6		6500	10.061	44.325	838.820	1047	3 S4P6	860	8.332	47.344		853.31
1 A4P8		1475	11.216	69.459	742.240	1049	1 S4P8	490	7.453	48.512		856.06
2 A4P8	-0.5	1250	11.363	69.312	738.510	1058	2 S4P8	640	7.955	51.713		838.22
3 A4P8		1550	11.127	65.995	769.230	1074	3 S4P8	544	8.098	53.093		836.63
1 A4P8		3850	10.573	54.222	821.510	1052	1 S4P8	1036	8.280	49.258		843.15
2 A4P8	0.0	3300	10.897	49.539	816.900	1032	2 S4P8	1584	7.850	43.737		876.39
3 A4P8		5500	10.604	50.411	829.960	1047	3 S4P8	2480	7.798	40.790		884.45
1 A4P8		2550	10.805	59.273	783.790	1052	1 S4P8	2664	7.816	33.519		900.33
2 A4P8	0.5	4750	11.105	58.485	810.780	1058	2 S4P8	2400	7.989	34.831		912.03
3 A4P8		4875	10.805	59.273	783.790	1052	3 S4P8	2160	8.220	44.317		867.48
1 A5P6		3200	10.468	25.534	781.18	909	1 S5P6	424	7.927	48.384		843.71
2 A5P6	-0.5	2900	10.723	39.783	690.46	864	2 S5P6	668	7.469	49.990		851.30
3 A5P6		3500	10.835	48.797	651.37	861	3 S5P6	764	7.517	48.195		852.17
1 A5P6		4125	10.710	42.101	698.30	876	1 S5P6	744	7.883	47.150		861.43
2 A5P6	0.0	1625	10.584	43.333	698.03	887	2 S5P6	888	7.605	47.644		857.71
3 A5P6		5750	10.166	48.614	704.55	942	3 S5P6	900	7.380	46.585		858.58
1 A5P6		3250	10.819	45.744	661.46	869	1 S5P6	2440	7.473	37.069		895.56
2 A5P6	0.5	3560	9.016	47.100	564.90	776	2 S5P6	1824	7.134	32.490		906.45
3 A5P6		3875	9.906	48.275	639.55	891	3 S5P6	3488	7.038	31.084		911.38
1 A5P8		2550	10.217	38.543	663.54	825	1 S5P8	672	7.445	57.682		835.79
2 A5P8	-0.5	2375	9.161	59.753	756.67	1016	2 S5P8	396	7.265	53.960		859.17
3 A5P8		4750	8.083	23.693	723.37	830	3 S5P8	512	7.656	56.813		842.73
1 A5P8		5625	7.171	24.845	711.25	836	1 S5P8	1020	7.460	51.417		853.31
2 A5P8	0.0	4125	9.798	54.522	773.04	1008	2 S5P8	1608	7.652	46.923		872.31
3 A5P8		3125	10.155	32.938	681.47	825	3 S5P8	1616	7.844	50.780		868.75
1 A5P8		1425	10.422	36.944	667.57	824	1 S5P8	2232	7.201	36.618		905.04
2 A5P8	0.5	4875	5.335	38.374	795.48	819	2 S5P8	6112	7.177	38.223		903.16
3 A5P8		5125	6.232	35.887	764.24	822	3 S5P8	4400	7.520	44.138		895.43
1 A4A6		444	6.119	39.965	778.64	959	1 S4A6	564	8.026	50.107		827.97
2 A4A6	-0.5	538	6.282	44.871	787.96	984	2 S4A6	326	7.435	46.117		832.25
3 A4A6		238	5.855	44.249	773.68	971	3 S4A6	426	7.723	50.088		811.04
1 A4A6		450	6.419	46.253	780.63	987	1 S4A6	888	8.312	54.104		809.26
2 A4A6	0.0	235	6.137	48.104	783.91	998	2 S4A6	544	7.693	46.870		830.14
3 A4A6		538	6.188	43.421	784.84	975	3 S4A6	1392	7.938	44.122		849.20
1 A4A6		906	6.716	44.815	776.91	983	1 S4A6	1408	8.073	46.509		847.04
2 A4A6	0.5	714	6.673	45.196	788.27	992	2 S4A6	1312	7.832	39.271		859.24
3 A4A6		1816	6.419	42.104	799.94	992	3 S4A6	3000	7.905	38.328		865.18
1 A4A8		1176	9.123	51.139	772.79	998	1 S4A8	324	6.868	44.123		829.01
2 A4A8	-0.5	1372	8.877	49.526	794.28	1005	2 S4A8	356	6.971	50.617		804.45
3 A4A8		1824	8.614	53.073	794.55	1029	3 S4A8	688	7.483	56.506		803.21
1 A4A8		1680	9.744	52.217	803.84	1026	1 S4A8	486	7.695	52.007		807.22
2 A4A8	0.0	2144	9.742	48.769	807.65	1013	2 S4A8	3616	7.386	31.991		862.23
3 A4A8		812	10.258	58.466	769.10	1023	3 S4A8	344	7.767	44.967		818.20
1 A4A8		2440	10.225	46.158	801.24	993	1 S4A8	900	8.264	45.079		856.14
2 A4A8	0.5	2448	6.204	44.110	799.73	992	2 S4A8	948	8.313	36.983		846.30
3 A4A8		840	6.811	46.144	787.61	992	3 S4A8	732	8.417	44.112		833.02
1 A5A6		1524	8.543	53.748	770.26	1008	1 S5A6	296	6.739	51.736		804.55
2 A5A6	-0.5	2024	8.157	55.907	785.50	1029	2 S5A6	324	6.780	52.890		801.58
3 A5A6		1424	8.900	58.416	780.06	1037	3 S5A6	350	6.532	52.481		814.92
1 A5A6		1416	9.648	58.161	775.22	1029	1 S5A6	440	7.541	46.088		828.54
2 A5A6	0.0	2480	9.622	53.063	802.01	1028	2 S5A6	600	7.364	44.679		833.53
3 A5A6		3928	9.256	45.210	872.15	1065	3 S5A6	560	7.895	52.836		812.41
1 A5A6		4024	8.632	40.233	832.11	1017	1 S5A6	728	8.487	48.941		804.52
2 A5A6	0.5	2544	9.064	41.651	830.60	1005	2 S5A6	824	7.312	46.536		830.80
3 A5A6		3376	8.979	47.587	813.47	1013	3 S5A6	1076	7.557	42.811		846.27
1 A5A8		2640	8.427	50.076	789.29	1007	1 S5A8	314	6.701	46.173		810.62
2 A5A8	-0.5	1888	8.665	55.004	789.63	1029	2 S5A8	380	6.786	51.148		789.57
3 A5A8		2744	8.038	53.134	798.62	1029	3 S5A8	378	7.298	50.725		793.20
1 A5A8		1640	9.026	46.620	821.98	1016	1 S5A8	728	8.685	55.412		791.73
2 A5A8	0.0	2312	8.931	48.718	814.79	1022	2 S5A8	724	7.788	48.103		819.08
3 A5A8		3392	8.909	52.352	802.56	1031	3 S5A8	740	8.096	51.413		809.47
1 A5A8		2776	9.547	38.051	824.58	983	1 S5A8	2128	8.447	51.536		814.41
2 A5A8	0.5	2344	9.217	34.710	835.80	984	2 S5A8	1264	8.699	53.506		812.96
3 A5A8		3344	9.325	40.075	819.42	986	3 S5A8	1144	9.188	54.484		793.68

Table 7 Parameters statistical analysis in SPSS 19 results

	Descriptive Statistics						
	N	Range	Minimum	Maximum	Mean	Std. Deviation	Variance
Flow Number	144	7140	235	7375	1954.76	1604.082	2573077.54
K	144	6.03	5.34	11.36	8.3890	1.37017	1.877
k ₁	144	77.83	-8.37	69.46	46.7772	9.99775	99.955

Table 8 Model statistical specification summary (SPSS 19 output)

Model Summary					
Model	R	R Square	Adjusted R Square	Std. Error of the Estimate	Change Statistics Sig. F Change
1	0.932	0.869	0.867	816.145	.000

Table 9 Model independent variable coefficient (SPSS 19 output)

Coefficients								
Model		Unstandardized Coefficients		Standardized Coefficients	T	Sig.	.95% Confidence Interval for B	
		B	Std. Error	Beta			Lower Bound	Upper Bound
1	k	743.562	39.843	2.816	18.662	0.000	664.743	822.382
2	k ₁	-94.115	6.993	-2.031	-13.459	0.000	-107.948	-80.282

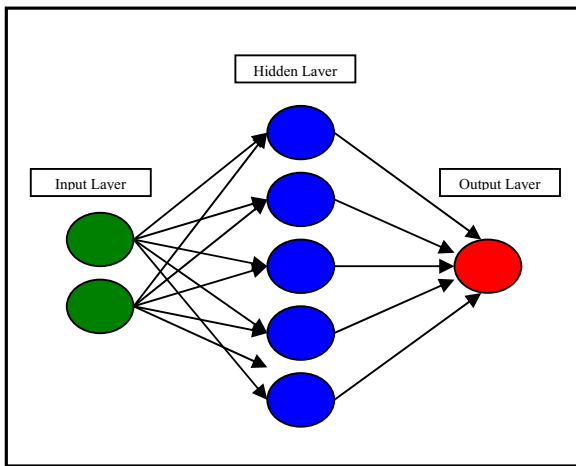


Fig. 6 ANN layers

Coefficients are modified based on this error. Whatever root mean square error (RMSE) is closer to zero, error is less, so the model is better.

$$RMSE = \sqrt{\frac{\sum_{i=1}^n (x_i - y_i)^2}{n}} \quad (8)$$

R² is the statistical index to validate output accuracy which

whatever closer to 1, more precise the model is.

$$R^2 = \left(\frac{\sum_{i=1}^n (x_i - \bar{x})(y_i - \bar{y})}{\sqrt{\sum_{i=1}^n (x_i - \bar{x})^2 \sum_{i=1}^n (y_i - \bar{y})^2}} \right)^2 \quad (9)$$

MATLAB 2008 software was use for coding the network. About 67% of data were used for training the network after normalizing by equation 10 and remained data were used for validation.

$$X_n = (x - x_{min}) / (x_{max} - x_{min}) \quad 0 \leq X_n \leq 1 \quad (10)$$

4.2.1. Neural Network results for presented model

Considering two neurons in input layer and one in output and using 5, 10, 15 and 20 neurons in median layers, results were obtained as table 10 and figure 8. R² were determined as 0.9122 in best structure in validation phase as it is stated in table.

4.3. Validating model Using GA

Genetic Algorithm (GA) is a method of optimizing and validating models which using a natural inception performs based on evolution principle (Survival of the fittest). GA applies survival fittest rule on a set of solutions to obtain better answers. Independent variables are determined in each phase of evolution so that less difference is achieved between real value of dependent variable and estimated value (Figure 9). MATLAB 2008 software was used for coding and Excel 2007 for comparing the results in this study.

4.3.1. GA results for presented model

As it is illustrated in figure 10, 0.835 is obtained as determination coefficient for this model.

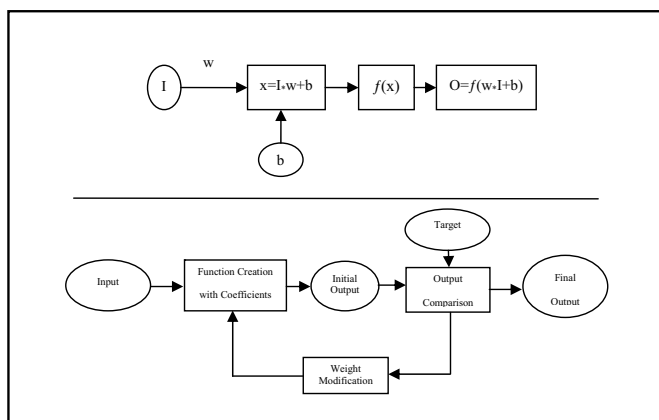


Fig. 7 Neural network architecture

Table 10 Neural network run output (for 5, 10, 15 and 20 neurons in a hidden layer)

Neural Network Structure	Training Phase		Validation Phase
	R ²	RMSE	R ²
2-5-1	0.8231	0.0162	0.7061
2-10-1	0.8117	0.0120	0.7861
2-15-1	0.8927	0.0102	0.8366
2-20-1	0.9270	0.00705	0.9122

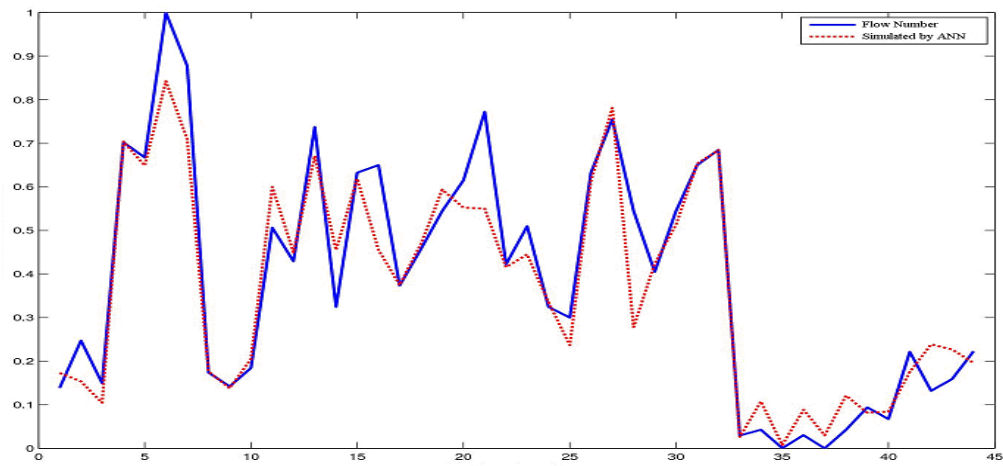


Fig. 8 Standardized flow number curve of model and real values in 1-20-2 structure of validating phase

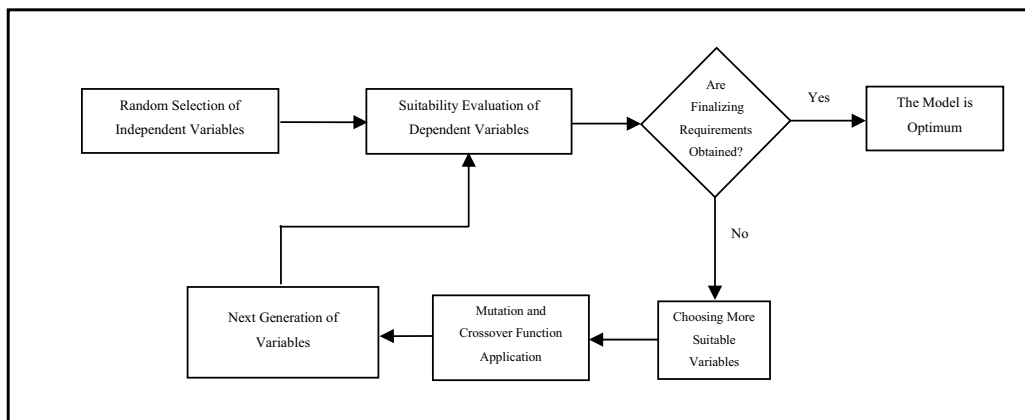


Fig. 9 Applied GA flowchart

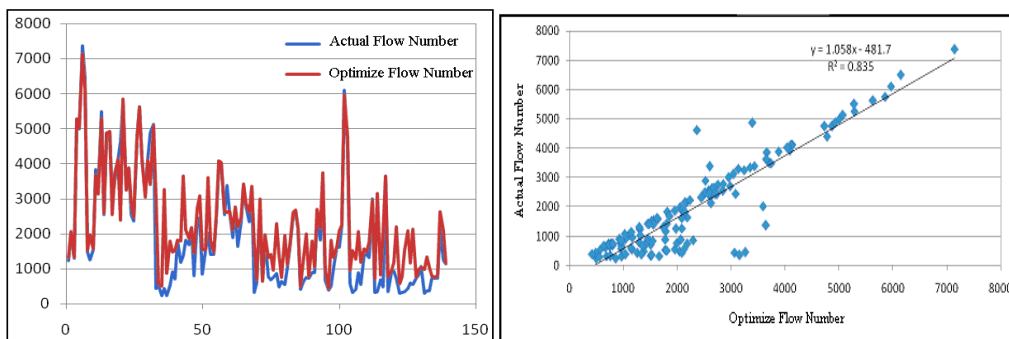


Fig. 10 a. Estimated and real values comparison of model number 1 during evolution and b. Regression on real and estimated values of model

5. Discussion and Conclusion

One of the most important consequences of this study is GSM shear stress modeling versus gyration number. It was proved that logarithmic model results in the best trend. This curve has two main phases. The first phase can be named as compaction phase, has an intense slope. Shear stress variation in this phase is more than condensation phase, as the second phase of the curve. Voids variation of first phase is more than

that of the second one too. Using the GSM compaction slope and equation slope the model for predicting flow number was developed. It should be noted the model is developed in 50°C and with OAC. Other conclusions are as following:

- In compaction phase, particle movement in various directions will cause asphalt compaction initially. But in second phase aggregates rotation and slippage lead to volume reduction and specimen density increase. So mixture voids are more in compaction slope in compare with condensation phase

considerably.

- Average compaction slope for specimens prepared with gradation #4 is more than #5 prepared specimens. Compaction slope is an index of aggregates internal friction. So #4 gradation which has more coarse aggregates has more compaction slope than #5 gradation.

- Shear stress variation in compaction phase is more than condensation phase. The reason will be for materials more impacts and a resistance to mixture volume change in this phase.

- Compaction slope coefficient is positive in the developed model. So specimens with higher compaction slope have more flow number and are resisted to rutting more. This is due to high resistance because of more internal friction and structural form. This is in accordance with other consequences about compaction slope.

- Shear stress curve negative coefficient in this model states asphalt mixtures with higher shear stress gradient in compaction phase are resisted to rutting more. In other words the more the shear stress in the compaction slope in compare with condensation phase is, the less the shear strength of mixture is.

- Using developed model, flow number can be estimated simultaneously during specimen preparation for determining OAC and evaluate rutting index before preparation, so a considerable save will be held in time and costs.

Acknowledgement:Writers are thankful of Technical and Soil Mechanic Laboratory Co and IUST ABRC personnel helping researchers during the study.

References

- [1] Ameri, M., MoghadasNejad, F., &Mirzahoseini, R. (2010). Presenting a Predicting Model for Asphalt Mixture Rutting Using Marshall Mix Design Method Paramteres and Studing These Parameters Effect on Flow Number.6thNational CongressonCivil Engineering, Ferdowsi University of Mashhad, Mashhad, Iran, 2010.
- [2] Wen, Y., Yong He, W., &Rui, Z. (2010). Study on Rutting of Asphalt Pavements. *Advanced Materials Research* , 1096-1099.
- [3] Drakos, C. (2003). Identification of A physical Model to Evaluate Rutting Performance of Asphalt Mixture. Florida: A dissertation presented to graduate school of the University of Florida in partial Fulfillment of the requirements for the degree of Doctor of Philosophy University of Florida.
- [4] Transportation Research Institute, (2010). Experimental Study of Gradation Type and VoidsEffect on Bleeding and Rutting in Asphalt Concrete in Iran. Tehran, Iran: Transportation Research Institute.
- [5] Santucci, L. (2000). Rut Resistant Asphalt Pavements, LTAP Field Engineer, Tech Transfer Program and Pavement Specialist, Pavement Research Center, UC Berkeley, Institute of Transportation Studies, 2000, pp. 1-8.
- [6] Hafeez, I., & Kamal, M. (2011). Repeated Load Permanent Deformation Behavior of Mixes. *Journal of Engineering and Technology*, 15-22.
- [7] Fujie , Z., Scullion, T., &Lijun, S. (2004). Verification and Modeling of Three-Stage Permanent Deformation Behavior of Asphalt Mixes. *Journal of Transportation Engineering* , 486-494.
- [8] Horak E, Emery S and Mihaljevic, I (2011) Balancing asphalt rut resistance with durability and safety requirements on runway

rehabilitations.Airfield Pavements Seminar, XXIVth World Road Congress, Mexico City, 28-29 Sept

- [9] Hai Fan, S., & Ling, L. (2011). Investigation on Countermeasures Analysis of Rutting in Highway Asphalt Concrete Pavement . *Advanced Materials Research, Advances in Civil Engineering*, 3263-3267.
- [10] Ameri, M., Moghadasnejad, F., &Mirzahoseini, R. (2009). The Effect of Gradation and VMA On Rutting Potential and Presenting Rutting Prediction Model. *Jaddeh Scientific Journal*, 5.
- [11] Mohammadzadeh, M., Latifi, M., &Mohammadzadeh, H. (2008). A Comparision Between Gytratory and Marshall Compaction Methods to Prepare Asphalt Mixtures for Evaluating Asphalt Behavior. 4th National Congress on Civil Engineering . Tehran, Iran: University of Tehran.
- [12] McGarvey, K., Panko, M., Hurt, C., Mehta, Y., &Sukunaran, B. (2010). Use of Superpave Gytratory Compactor as a Predictor of Field Performance. FAA Worldwide Airport Technology Transfer Confecece . Atlantic City, NewJersey, USA.
- [13] Corte, J., &Serfass, J. (2000). The French Approach to Asphalt Mixture Design: A Performance Related System of Specification . Association of Asphalt Paving Technologists.
- [14] Anderson, R., Christensen, W., &Bonaquist, R. (2003). Estimating the Rutting Potential of Asphalt Mixtures Using Superpave Gytratory Compaction Properties and Indirect Tensile Strength. Association of Asphalt Paving Technologists- Proceeding of the Technical Sessions.
- [15] Roque, R., Birgisson, B., Darku, D., &Darkos, C. (2004). Evaluation of Laboratory Testing System for Asphalt Mixture Design and Evaluation.
- [16] Archilla, A. (2006). Use of Superpave Gytratory Compaction Data for Rutting Prediction . *Journal of Transportation Engineering*.
- [17] You, Z., & Barak, J. (2009). Development of Specification for the Superpave Simple Performance Tests (SPT). Michigan: Department of Civil and Environmental Engineering Michigan Technological University.
- [18] LubindWalubita, F., Umashankar, V., Hu, X., Jamison, B., Zhou, F., Scullion, T., Martin, A.E., &Dessouky, S. (2010). New Generation on Mix-Designs: Laboratory Testing and Construction of The APT Test Sections, Texas Department of Transportation and theFederal Highway Administration, Project No.: FHWA/TX-10/0-6132-1, March 2010.
- [19] Office of Deputy for Strategic Supervision, The Ministry of Roads and Urban Development, (2011), Iran Highway Asphalt Paving Code No. 234.
- [20] Dessouky, S., Walubita, L., Urnashankar, V., Hu, X., Jamison, B., Zhou, F., et al. (2010). New Generation Mix-Designs: Laboratory Testing and Construction of the APT Test Sections. Texas: Texas Transportation Institute-Project 0-6132.
- [21] Standard, A. (2009). Methods of Sampling and Testing Asphalt, Method 12-: Determination of the Permanent Compressive Strain Characteristics of Asphalt-Dynamic Creep Test.
- [22] Hua Hu, C. (2011). Prediction of Resilient Modulus for Hot Mix Asphalt Based on Artificial Neural Network. *Advanced Materials Research*, 18-23.
- [23] Sakhaeifar, M., Underwood, S., Kim, R., Puccinelli, J., & Jackson, N. (2010). Development of Artificial Neural Network Models for Populating Dynamic Module of Long-Term Pavement Performance Section. *Transportation Research Record*, 88-97.
- [24] Morova, S. S., Terzi, N., &Sargin, S. (2011). Amount of Bituminous Effects on Asphalt Concrete Strength with Artificial Intelligence and Statistical Analysis Method. *International Symposium on Innovations in Intelligent Systems and Applications* , (pp. 329-334).
- [25] Beainy, F., Commuri, S., &Zaman, M. (2010). Asphalt Compaction Quality Control Using Artificial Neural Network . 49th IEEE Conference on Decision and Control (CDC), (pp. 4643-4648).